

Vol. 2 No. 1 Juni 2010

ISSN: 2085 - 6695

**e-Jurnal**

**Ilmu dan Teknologi  
Kelautan Tropis**



Departemen Ilmu dan Teknologi Kelautan  
Fakultas Perikanan dan Ilmu Kelautan  
Institut Pertanian Bogor  
[http://www.itk.fpk.ipb.ac.id/ej\\_itk21](http://www.itk.fpk.ipb.ac.id/ej_itk21)

**Vol.2, No.1, Juni 2010**

**ISSN: 2085-6695**

**Elektronik Jurnal**  
**ILMU DAN TEKNOLOGI KELAUTAN TROPIS**



**DEPARTEMEN ILMU DAN TEKNOLOGI KELAUTAN**

**FAKULTAS PERIKANAN DAN ILMU KELAUTAN**

**INSTITUT PERTANIAN BOGOR**

**[http://www.itk.fpik.ipb.ac.id/ej\\_itkt21](http://www.itk.fpik.ipb.ac.id/ej_itkt21)**

## **E-Jurnal Ilmu dan Teknologi Kelautan Tropis**

Diterbitkan oleh : Departemen Ilmu dan Teknologi Kelautan  
Fakultas Perikanan dan Ilmu Kelautan  
Institut Pertanian Bogor

Penanggung Jawab : Ketua Departemen Ilmu dan Teknologi Kelautan

Pemimpin Redaksi : Bisman Nababan, Ph.D.

Penyunting Ahli :

Agus Supangat, Ph.D. (Ocean Dynamic, Climate Change, BRKP-DKP)  
Bambang Yulianto, Ph.D. (Marine Ecotoxicology, FPIK-UNDIP)  
Prof. Dr. Bonar Pasaribu (Marine Acoustic, ITK-IPB)  
Prof. Dr. Feliatra (Marine Microbiology, ITK-UNRI)  
Henry Manik, Ph.D. (Marine Acoustic, ITK-IPB)  
Inneke Rumengan, Ph.D. (Marine Biotechnology, FPIK-UNSRAT)  
Iqbal Djawad, Ph.D. (Marine Aquaculture & Physiology., FIKP-UNHAS)  
John I. Pariwono, Ph.D. (Physical Oceanography, ITK-IPB)  
Joko Santoso, Ph.D. (Aquatic Product Processing Technology, THP-IPB)  
Dr. Jonson L. Gaol (Marine Remote Sensing & GIS, ITK-IPB)  
Prof. Dr. Mulia Purba (Physical Oceanography, ITK-IPB)  
Neviaty P. Zamani, Ph.D. (Marine Biology, Coral Reef, ITK-IPB)  
Richardus Kaswadji, Ph.D. (Biological Oceanography, ITK-IPB)  
Wahyu Pandoe, Ph.D. (Physical Oceanography, Modeling, BPPT)  
Prof. Dr. Setyo Budi Susilo (Marine Remote Sensing & CZM, ITK-IPB)  
Zainal Arifin, Ph.D. (Marine Pollution, Chemical Oceanography, P2O-LIPI)  
Tri Prartono, Ph.D. (Chemical Oceanography, ITK-IPB)

Penyunting Pelaksana : Risti Endriani Arhatin, M.Si.  
Meutia Samira Ismet, M.Si.  
Sri Ratih Deswati, M.Si.  
Sahat M.R. Tampubolon, Amd.

Alamat Redaksi : Departemen Ilmu dan Teknologi Kelautan, FPIK  
Jl. Lingkar Akademik  
Kampus IPB Darmaga, Bogor 16680  
Jawa Barat  
e-mail: simson\_naban@yahoo.com

*Isi dapat dikutip dengan menyebutkan sumbernya*

## KATA PENGANTAR

Puji syukur kehadiran Tuhan Yang Maha Kuasa atas rahmat-Nya sehingga E-Jurnal Ilmu dan Teknologi Kelautan Tropis Volume 2 Nomor 1 ini dapat terbit.

Melalui seleksi dan review oleh tim reviewer, dari sejumlah paper yang masuk sebanyak 6 (enam) paper dapat diterima dengan perbaikan untuk diterbitkan pada edisi ini dengan judul sebagai berikut: (1) Study on Biorock® Technique Using Three Different Anode Materials (Magnesium, Aluminum, and Titanium); (2) Kelimpahan Foraminifera Resen pada Sedimen Permukaan di Teluk Ambon ; (3) Pemetaan Substrat Dasar Perairan Dangkal Karang Congkak dan Lebar Kepulauan Seribu Menggunakan Citra Satelit Quick Bird; (4) Model Dispersi Bahang Hasil Buangan Air Proses Pendinginan PLTGU Cilegon CCPP ke Perairan Pantai Margasari di Sisi Barat Teluk Banten; (5) Pemetaan dan Analisis Index Vegetasi Mangrove Di Pulau Saparua, Maluku Tengah; dan (6) Efek Ukuran Butiran, Kekasaran, dan Kekerasan Dasar Perairan Terhadap Nilai Hambur Balik Hasil Deteksi Hydroakustik.

Semoga E-Jurnal Ilmu dan Teknologi Kelautan Tropis ini dapat meningkatkan diseminasi dan ketersediaan informasi akan hasil-hasil penelitian di bidang ilmu dan teknologi kelautan tropis. Kiranya juga E-Jurnal ini bermanfaat untuk pengembangan dan kemajuan ilmu dan teknologi kelautan tropis.

Pemimpin Redaksi

## DAFTAR ISI

<b>STUDY ON BIOROCK® TECHNIQUE USING THREE DIFFERENT ANODE MATERIALS (MAGNESIUM, ALUMINUM, AND TITANIUM)</b> <i>(THE ABUNDANCE OF RECENT FORAMINIFERA IN SURFACE SEDIMENT OF AMBON BAY)</i>	
<b>N. P. Zamani, R. Bachtiar, H. H. Madduppa, J. W. Adi, J. Isnul, M. Iqbal, and B. Subhan .....</b>	<b>1</b>
<b>KELIMPAHAN FORAMINIFERA RESEN PADA SEDIMEN PERMUKAAN DI TELUK AMBON</b> <i>(THE ABUNDANCE OF RECENT FORAMINIFERA IN SURFACE SEDIMENT OF AMBON BAY)</i>	
<b>Suhartati M. Natsir .....</b>	<b>9</b>
<b>PEMETAAN SUBSTRAT DASAR PERAIRAN DANGKAL KARANG CONGKAK DAN LEBAR KEPULAUAN SERIBU MENGGUNAKAN CITRA SATELIT QUICK BIRD</b> <i>(THE BOTTOM SUBSTRATE SHALLOW WATER MAPPING USING THE QUICK BIRD SATELLITE IMAGERY)</i>	
<b>Vincentius Siregar .....</b>	<b>19</b>
<b>MODEL DISPERSI BAHANG HASIL BUANGAN AIR PROSES PENDINGINAN PLTGU CILEGON CCPP KE PERAIRAN PANTAI MARGASARI DI SISI BARAT TELUK BANTEN</b> <i>(THERMAL DISPERSION MODEL OF WATER COOLING PLTGU CILEGON CCPP DISCHARGE INTO MARGASARI COASTAL WATERS AT THE WESTERN COAST OF BANTEN BAY)</i>	
<b>I Wayan Nurjaya dan Heron Surbakti.....</b>	<b>31</b>
<b>PEMETAAN DAN ANALISIS INDEX VEGETASI MANGROVE DI PULAU SAPARUA, MALUKU TENGAH</b> <i>(MAPPING AND INDEX VEGETATION ANALYSES OF MANGROVE IN SAPARUA ISLAND, CENTRAL MOLUCCAS)</i>	
<b>Harold J. D. Waas dan Bisman Nababan.....</b>	<b>50</b>
<b>EFEK UKURAN BUTIRAN, KEKASARAN, DAN KEKERASAN DASAR PERAIRAN TERHADAP NILAI HAMBUR BALIK HASIL DETEKSI HYDROAKUSTIK</b> <i>(EFFECTS OF GRAIN SIZE, ROUGHNESS, AND HARDNESS OF SEA FLOOR ON BACK SCATTERING VALUE BASED ON HYDROACOUSTIC DETECTION)</i>	
<b>Sri Pujiyati, Sri Hartati, dan Wijo Priyono .....</b>	<b>59</b>

## STUDY ON BIOROCK® TECHNIQUE USING THREE DIFFERENT ANODE MATERIALS (MAGNESIUM, ALUMINUM, AND TITANIUM)

Neviaty P. Zamani<sup>1\*)</sup>, Ramadian Bachtiar<sup>1</sup>, Hawis H. Madduppa<sup>1</sup>, Jhoni Wahyu Adi<sup>2</sup>, Jeddah Isnul<sup>1</sup>, Muhamad Iqbal<sup>1</sup>, and Beginer Subhan<sup>1</sup>

1. Department of Marine Science and Technology, Faculty of Fisheries and Marine Science, Bogor Agricultural University, Jl. Agatis No.1, Bogor 16680, Indonesia
  2. Department of Metallurgy and Materials, Faculty of Mathematics and Science, University of Indonesia, Depok 16424, Indonesia
- \*E-mail: [np\\_zamani@yahoo.com](mailto:np_zamani@yahoo.com).

### ABSTRACT

Biorock® technique is the earliest methods to rehabilitate the damage of coral reef ecosystem. Its improvement is need to carry on since it is subject to some inhibitions in particular the dependence of expensively-imported Titanium (Ti) as the anode materials. The main purpose of this research was to find the best anode material as a possible substitution which can be economically and easily to apply in Indonesia. Therefore we compared Titanium (Ti) with two other potential anodes material (Magnesium-Mg, and Aluminum (Al)). The laboratory study was carried out for two days period (48 hours) in the stagnant sea water aquaria. Four aquarium tanks were treated by different electric current treatment (1 Ampere, 2 Ampere, 3 Ampere, and 5 Ampere, respectively). The reduction of electrode weigh (anode and cathode) was measured. During the experiment, water quality (i.e. pH, and salinity) and mineral waters (calcium) were collected every 6 hour in 48 hours. The solid form of calcium carbonate was analyzed using XDS (X-ray Dispersion Spectrophotometer). The accretion rates on cathode and anode decay were compared between anodes which were treated by different electrical current. Based on the study, three anodes (aluminum, magnesium and titanium) showed different respond. Titanium and Magnesium anode showed electric current affected accretion rate ( $P < 1$ ), while for aluminum anode showed no differences on treatments.

**Keywords:** mineral accretion, Biorock®, anode, coral reef rehabilitation, accretion rate, anode decay rate, mineral uptake

### I. INTRODUCTION

Biorock® is using mineral accretion process and one of coral reef rehabilitation methods since late 1990s in Indonesia, which developed by Thomas Goreau, a marine biologist and Wolf Hilbertz, an engineer and architect (Hilbertz, 1979 and 1991; Bachtiar, 2003). Mineral accretion process is applying a low voltage direct electrical current through electrodes causing mineral crystals naturally found in seawater, mainly calcium carbonate and magnesium hydroxide, to grow on the structure (Hilbertz, 1979; Hartt 1984). The composite of limestone and brucite which found on the structure is similar to

the composition of natural coral reefs (Lee, 2002). This solid mineral is a byproduct of pH changes in the cathode during the electrolysis process of sea water (Hilbertz and Goreau, 1996). This method is furthermore increase coral reef growth 3-5 times faster than the normal conditions (Lee, 2002). The associations between organisms in that structure is faster and more diverse for certain case and even can be ten times faster (Faraday, 2004).

Anode material is one of the most important parts to apply Biorock® structure. Anode defined as the electrode where the electrons come from the cell and oxidation occurs (Hastatiningsih, 1997). Anode connected to the positive

terminal of power supply and a terminal where electrons taken from the ions in solution to facilitate chemical reactions. If the current is too high, the anode will corrode quickly (Hilbertz and Goreau, 1996). Anode material used in Biorock® structure should have high resistance to corrosion processes and have a high level of polarity due to the occurrence of oxidation reactions. In addition, pH values around the anode are acidic, which is potential to generate corrosion at iron, as cathode.

Titanium used as anode for the structure since its application (Lee, 2002). However, its improvement is needed to carry on since it is subject to some inhibitions in particular the dependence of expensively-imported Titanium (Ti) as the anode materials in Indonesia.

The main purpose of this research was to find the best anode material as a possible substitution which can be economically and easily to apply in Indonesia. Therefore we investigated the feasibility of Titanium (Ti) with two other potential anodes material (Magnesium-Mg, and Aluminum-Al), and treated in a different current density (1 Ampere, 2 Ampere, 3 Ampere, and 5 Ampere).

## II. METHOD

### 2.1. Preparation

The preparations of the research are the following steps: (1) The iron stick was burnished in order to clearance the rust; (2) anode materials preparations and productions (Figure 1); (2) Wire setting on two electrodes (cathode and anode); (3) Tip of the cathode was rubbed with Resin in order to avoid corrode and the two edge of iron stick would not be covered by  $\text{CaCO}_3$  deposit; (4) Electrode numbering; and (5) Electrode weighing.

### 2.2. Experiment set-up

Cathode and anode was set on rounded wooden skeleton like a rack with space for cathode and anode on it. Anode was set on the center, and cathodes were set surround the anode with the same interval (Figure 2, left).

Each cathode wire was combined and connected to negative terminal of power supply, and anode wire was connected to positive terminal of power supply. Each wire was shield by tape. The electric current's setting and measuring was conducted after all devices submerged in the aquarium filled with sea water (Figure 2, right).

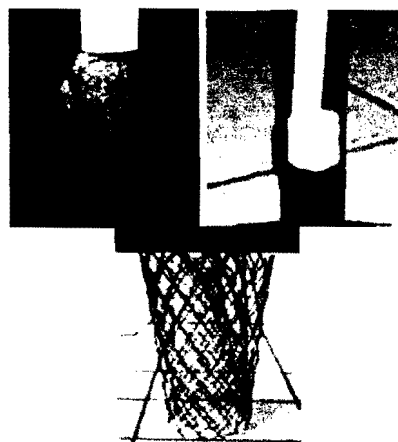


Figure 1. Anode materials used for the Biorock experiment (*left*: Aluminum, *middle*: Magnesium, *right*: Titanium)

### 2.3. Observation and data collection

The research was carried out for 3 months period (January to March 2006) at the Laboratory of Marine Biology, Department of Marine Science and Technology, Bogor Agricultural University. The experiment was carried out for two days (48 hours) in four aquariums, which filled with sea water and no current. Each aquarium was applied in different electric current (1

Ampere, 2 Ampere, 3 Ampere, and 5 Ampere). Data was collected every 12 hours start from  $t_0$  (starting time) with no repetition. pH values were measured during the experiment.

Sample of sea water in the aquaria was collected to monitor the composition of Ca and Mg during the experiment. Water sample were put in the glass bottle and three drops of  $\text{HNO}_3$  added as sea water preservation. Then glass bottle sample was wrapped by aluminum foil paper and kept in room temperature for

further analysis. Sample analysis using AAS was conducted in Environment Laboratory of Bogor Agricultural University.

Mineral solid form as accretion product was collected as dry material after 12 hours and weighted. Sample of mineral solid was collected for further mineral analysis in Metallurgy Laboratory-University of Indonesia by using XDS (X-ray Dispersion Spectrophotometer).

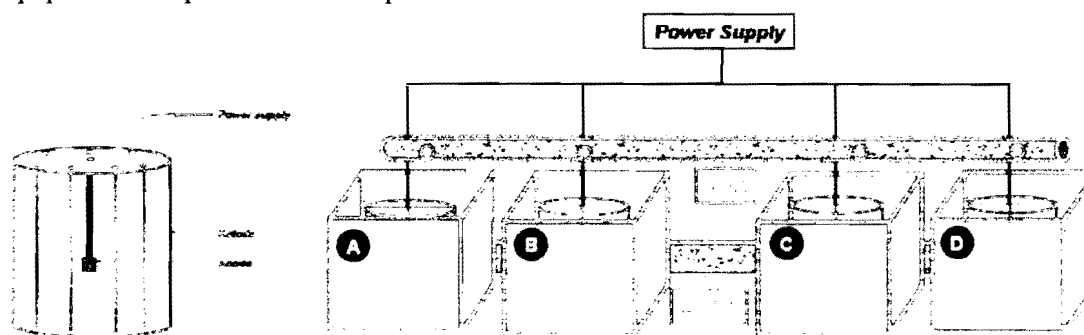


Figure 2. Schematic of electrode setting on wooden skeleton (*left*); and experiment set-up system in four identical aquariums which treated different electrical current from power supply (*right*).

## 2.4. Statistical analysis

Mineral solid weight and decay rate were calculated based on the value before and after experiment in the cathode and the anode, respectively. The mineral solid weight formed and anode decay rate parameters were compared using Randomized Complete Block Design, continued with ANOVA (Analysis of Variant) and Least Significance Difference using Statistica 7 (Ashworth and Booker, 1986).

## III. RESULTS AND DISCUSSION

### 3.1. pH variability

Changes of pH value rapidly occur in experiment treated large electrical

current. This is can be found on 3 Amp and 5 Amp, while on 1 Amp and 2 Amp was slower in changes.

Sea water pH in the aquarium had a significant change. At the titanium and aluminum anode, pH had decreased from about 8 to 6. However, the magnesium anode pH had tends to increased, ranged from 8.1 to 8.9 (Figure 3).

pH decreasing which occurred in titanium and aluminum anode because the concentration of increasing  $[\text{H}^+]$  and the formation of acid. This was come from derived carbonic acid fraction and the reaction at the anode. In the ocean occurs carbonate system which maintaining the pH of sea water in the buffer conditions. However, in a closed and limited system (e.g. aquarium), buffer conditions would not happen.



Therefore, there is a change of pH seawater.

Changes in pH are the result of the occurrence of electrolysis reaction at the electrode (cathode and anode). Reaction at the cathode was reduction and an alkaline, because of release  $[\text{OH}^-]$ . As for what happened in the anode were the oxidation reaction and an acid because it releases  $[\text{H}^+]$ . Consequently, more acidic conditions predominate in the aquarium.

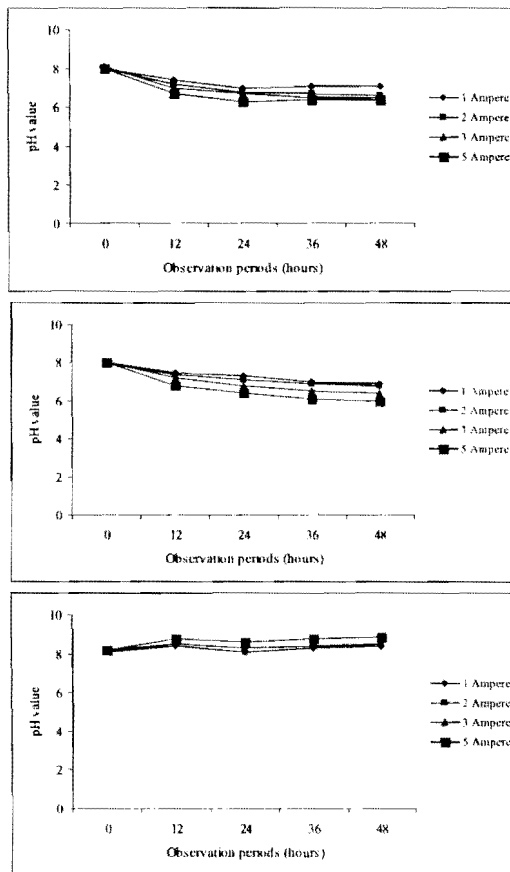


Figure 3. pH variability in the aquaria with Titanium anode (*above*), Aluminum anode (*middle*), and Magnesium anode (*below*), treated on four different electric current (1, 2, 3 and 5 Ampere).

### 3.2. Calcium and Magnesium uptake

Ca and Mg uptake value generally showed decreased on each anode (Titanium, aluminum, and Magnesium) during observation period (Figure 4 and Figure 5). The rising values of Ca uptake were on 3 Ampere at Aluminum anode, 1 Amp Magnesium anode and of Mg uptake was on 1 Amp Magnesium anode. Decreased value of Ca and Mg were caused by this materials were used in mineral accretion process. It applies an electric charge, causing dissolved minerals (Mg and Ca) to crystallize on the iron stick (cathode). Ca uptake on titanium anode ranged between 500 – 800 mg/L and Mg uptake ranged between 140 – 160 mg/L.

### 3.3. Mineral element composition

Magnesium hydroxide and calcium carbonate are one of the main components of Biorock®. This composition is essentially the result of the ionic composition of seawater. Comparison between mineral compositions, Magnesium (Mg) and Calcium (Ca), which crystallized on the cathode, is shown on Figure 6. In general, Mg composition much more dominant than Ca on each anode samples (titanium and magnesium). This is similar to reef composition. Reef as a control for the experiment showed ratio between Mg and Ca is 2:1. Ratio of Mg:Ca which closer to reef composition is on titanium with 1A (2:1). As on titanium with 2A dan 3A is 5:1 and 6:1, respectively. On Magnesium anode showed ratio with 1A, 2A and 3A is 4:1, 9:1 and 33:1, respectively.