



Journal of

# TROPICAL FOREST SCIENCE

Volume 18 Number 4

# JOURNAL OF TROPICAL FOREST SCIENCE

An international refereed journal published quarterly by the Forest Research Institute Malaysia

For correspondence and editorial enquiries relating to submission of papers and to journal subscription, please e-mail or write to:

K. A. Sarifah  
Forest Research Institute Malaysia (FRIM)  
52109 Kepong  
Selangor Darul Ehsan  
Malaysia

*Editors* : K. A. Sarifah (sarifah@frim.gov.my) & Y. F. Ho (hoyf@frim.gov.my)  
*Consulting editor*: F. S. P. Ng (fng@pc.jaring.my)

## EDITORIAL ADVISORY BOARD

### **M. A. Abdul Razak**

Forest Research Institute Malaysia, 52109 Kepong, Selangor Darul Ehsan, Malaysia. razak@frim.gov.my

### **P. S. Ashton**

Harvard Herbaria, 22 Divinity Avenue, Harvard University, Cambridge, Massachusetts 02138, USA.  
pashton@oeb.harvard.edu

### **P. Baas**

National Herbarium Nederland, P. O. Box 9514, 2300 RA Leiden, The Netherlands. Baas@nhn.leidenuniv.nl

### **K. M. Bhat**

Kerala Forest Research Institute, Peechi 680 653, Kerala, India. kmbhat@kfri.org

### **P. R. Crane**

Royal Botanic Gardens, Kew, Richmond, Surrey TW9 3AB, UK. p.crane@kew.org

### **D. P. Dykstra**

PNW Research Station, USDA Forest Service, 620 SW Main Street, Suite 400, Portland, OR 97205-3028, USA.  
ddykstra@fs.fed.us

### **S. A. Harris**

Druce Curator of Oxford University Herbaria, Department of Plant Sciences, University of Oxford, South Parks Road, Oxford, X1 3RB, UK. stephen.harris@plants.ox.ac.uk

### **C. Harwood**

Ensis Genetic, Private Bag 12, Hobart, Tasmania 7001, Australia. Chris.Harwood@ensisjv.com

### **P. Houghton**

Department of Pharmacy, King's College London, Franklin-Wilkins Building, 150 Stamford Street, London SE1 9NN, UK.  
peter.houghton@kcl.ac.uk

### **N. E. Koch**

Forest and Landscape Denmark, Skov and Landskab, Hoersholm Kongevej 11, 2970 Hoersholm, Denmark. nek@kvl.dk

### **F. E. Putz**



## CHEMICAL AND MECHANICAL WEARING OF HIGH SPEED STEEL AND TUNGSTEN CARBIDE TOOLS BY TROPICAL WOODS

W. Darmawan<sup>1,\*</sup>, I. S. Rahayu<sup>1</sup>, C. Tanaka<sup>2</sup> & R. Marchal<sup>3</sup>

<sup>1</sup>Faculty of Forestry, Bogor Agricultural University (IPB), Kampus IPB Darmaga, Bogor, Indonesia

<sup>2</sup>Faculty of Agriculture, Kagoshima University, Japan

<sup>3</sup>Department of Material and Process Laboratory, ENSAM CLUNY, France

Received December 2005

**DARMAWAN, W., RAHAYU, I. S., TANAKA, C. & MARCHAL, R. 2006. Chemical and mechanical wearing of high speed steel and tungsten carbide tools by tropical woods.** This paper presents the chemical and mechanical wearing of high speed steel and tungsten carbide tools by some tropical woods. In the first part of the experiment, weight losses of tool materials of JIS SKH51-A, JIS SKH51-H and JIS WC-12%Co after reacting with wood extracts of coconut, oil palm, teak, red meranti and pasang were studied. In the second part, the amount of wear on the clearance face of AISI M2, AISI K5 and AISI K10 tungsten carbide bits was measured when routing these woods. The tools suffered highest percentage of weight loss when soaked in both the extractive and wood powder solution of pasang. The WC-12%Co suffered smaller percentage of weight loss compared with SKH51-A and SKH51-H. The SKH51-A suffered slightly higher percentage of weight loss than SKH51-H. The bits suffered the largest clearance wear and wear rate when used for routing oil palm wood. The wear of M2 bit was twice larger than that of K5 and K10 when routing the same wood species.

Keywords: routing, extractive, silica, weight loss, clearance wear, tool bit

**DARMAWAN, W., RAHAYU, I. S., TANAKA, C. & MARCHAL, R. 2006. Penghausan kimia dan mekanik bahan pisau keluli dan karbida tungsten yang beroperasi pada kelajuan tinggi oleh kayu tropika.** Kertas kerja ini mengkaji penghausan bahan pisau-pisau keluli dan karbida tungsten pada kelajuan tinggi oleh beberapa kayu tropika. Penghausan kimia dan mekanik dikaji. Dalam bahagian pertama uji kaji, kehilangan berat bahan pisau JIS SKH51-A, JIS SKH51-H dan JIS WC-12% Co disukat selepas tindak balas dengan ekstrak-ekstrak kayu kelapa, kayu kelapa sawit, kayu jati, kayu meranti merah dan kayu pasang. Dalam bahagian kedua, jumlah haus pada mata bit AISI M2, AISI K5 dan AISI K10 disukat selepas ia digunakan untuk memotong kelima-lima kayu di atas. Bahan pisau yang direndam dalam ekstrak dan larutan habuk kayu pasang mengalami peratusan kehilangan berat yang paling banyak. Bahan pisau WC-12% Co mengalami peratusan kehilangan berat yang lebih rendah berbanding dengan SKH51-A dan JIS SKH51-H. Kehilangan berat pada SKH51-A lebih tinggi daripada JIS SKH51-H. Mata bit mengalami haus yang paling besar apabila digunakan untuk memotong kayu kelapa sawit. Bit M2 mengalami jumlah haus dua kali lebih besar berbanding dengan bit K5 dan K10 apabila memotong kayu yang sama.



High speed steel and tungsten carbide cutting tools are widely used in the woodworking industry in Indonesia for machining both natural and plantation woods which are mostly high in extractives and ash content. Extractives, that are found in the heartwood, are extractable with neutral organic solvents (ethanol, acetone, benzene, dichlorobenzene) and/or water.

About 400 wood species are commercially processed for wood construction and wooden furniture in Indonesia. A few studies on chemical components of some Indonesian commercial wood species have been done. It was reported that the extractive contents ranged from 1.4 to 13.8% by weight and the ash contents ranged from 0.1 to 5.0% by weight (Martawijaya *et al.* 1989).

Woods are usually machined before use in construction or furniture making. The machining required, when wood is cut, planed and shaped into useful products, is a significant cost factor in the wood products industry. Despite the extensive use of cutting tools in the wood industry, knowledge of their wearing characteristics on Indonesian wood is limited.

A study was conducted to investigate the effects of selected Indonesian woods on the chemical and mechanical wear characteristics of high speed steel and tungsten carbide cutting tools.

## MATERIALS AND METHODS

In the first part of the study, the following procedures were performed to investigate the interaction between wood extractives and cutting tool materials.

Ethanol/benzene extractives were extracted from 8 g of 50 mesh wood powders of coconut (*Cocos nucifera*), oil palm (*Elaeis guineensis*), teak (*Tectona grandis*), red meranti (*Shorea* sp.) and

weight. The TAPPI T211 om-85 procedures were then applied to determine the ash and silica content of these woods (TAPPI 1991b). The acidity (pH) of wood samples was determined by dissolving 5 g of 50 mesh wood powders in 50 ml distilled water. The solution was heated on the water bath for about 30 min until it reached 80 °C. After cooling, the pH of the solution was measured by using the pH meter. In order to produce 3 g of dry solid extracts, the extraction process was made repeatedly. However, this was only performed for red meranti and pasang. Extractive solution of 10% was prepared by dissolving 1 g of dry solid extract of red meranti and pasang in each 10 ml distilled water. New tips of annealed SKH51 (SKH51-A), hardened SKH51 (SKH51-H) and WC-12%Co (Table 2), which were characterized by Japan Industrial Standard (JIS), were reacted with the prepared extractive solutions in a stirred slurry. The mixtures were allowed to react for 48 hours at 80 °C. After that, the tips of the tool materials were cleaned with chloroform and dried, and the weight losses were determined.

Wood powders of 50 mesh were prepared from coconut, oil palm, teak, red meranti and pasang (Table 1). New tips of the tool materials were soaked in stirred slurry containing 100 ml hot water and 20 g wood powder of each wood species. The mixtures were allowed to react for 48 hours at 80 °C. After that, the tips were rinsed with chloroform to remove any residue wood powder and dried. The weight losses were determined.

In the second part of the study, wood samples were routed in up milling direction (feeding direction of wood samples counter rotation direction of the router spindle) on the Computer Numerical Control (CNC) Router using M2 high speed steel, K5 and K10 tungsten carbide bits, which were characterized according to American

in Figure 1. The amount of wear on the clearance face of the bits was measured every 7 min cutting time up to 70 min cutting time. The method for the wear measurement was described in the previous paper (Darmawan *et al.* 2001a). The wear patterns were also characterized under an optical video microscope.

## RESULTS AND DISCUSSION

### Chemical wearing of tool materials

Extractive and silica contents in the woods, and the percentage of weight loss of the tool materials after 48 hours reaction at 80 °C are presented in Tables 5 and 6 respectively. The amount of chemical wear was determined by the percentage of weight loss of the tool materials. Table 5 shows that the woods tested are acidic and vary slightly in extractive content. Oil palm had the highest silica content.

The tool materials suffered the highest percentage of weight loss when they were soaked

**Table 2** Specifications of cutting tool materials

| Tool material                          | Specification  |   |  |                |
|--|----------------|---|--|----------------|
|  | Dimension      | Metal component (% wt)  | Heat treatment   | Hardness (HRA) |
| JIS<br>Annealed SKH51 (JIS<br>SKH51-A) | 2 × 10 × 20 mm | Fe = 81.63, C = 0.88,<br>Si = 0.25, Mn = 0.30,<br>Cr = 4.04, W = 6.13,<br>Mo = 4.92, V = 1.85 | Annealed at 900 °C   | 61.5           |
| JIS<br>Hardened SKH51 (JIS<br>SKH51-H) | 2 × 10 × 20 mm | Fe = 81.63, C = 0.88,<br>Si = 0.25, Mn = 0.30,<br>Cr = 4.04, W = 6.13,<br>Mo = 4.92, V = 1.85 | Hardened at 1220 °C<br>followed by two times<br>of one hour tempering<br>at 560 °C | 83.7           |
| JIS K30 Tungsten<br>carbide            | 2 × 10 × 20 mm | WC = 88, Co = 12  | –  | 88.5           |

**Table 3** Specifications of router bits

| Specification        | Router bits                 |                          |                           |
|----------------------|-----------------------------|--------------------------|---------------------------|
|                      | AISI M2 high speed steel    | AISI K5 tungsten carbide | AISI K10 tungsten carbide |
| Bit diameter         | 12 mm                       | 12 mm                    | 12 mm                     |
| Number of knives     | 2                           | 2                        | 2                         |
| Rake angle           | 10°                         | 10°                      | 10°                       |
| Clearance angle      | 15°                         | 15°                      | 15°                       |
| Hardness             | 83.9 HRA                    | 93.1 HRA                 | 92.5 HRA                  |
| Thermal conductivity | 25 W/m.K                    | 100 W/m.K                | 80 W/m.K                  |
| Metal composition    | Almost same as JIS<br>SKH51 | WC-5%Co                  | WC-6%Co                   |



in both extractive and wood powder solution of pasang, although the amounts of extractive per unit oven dry volume were almost the same with other woods (Table 6). This indicated that the chemical compounds in pasang were more reactive to elements in the tool materials. The percentages of weight loss were larger in extractive soaking than in the wood powder soaking for both pasang and red meranti (Table 6).

The SKH51 tool materials suffered a higher percentage of weight loss compared with tungsten carbide for all wood species. This is a result of the wide variety of metal components in SKH51, which were susceptible to chemical attack rather than the unvaried compound of WC and Co in the tungsten carbide (Table 2).

The SKH51-H, which underwent complete heat treatments (annealing, austenitizing, quenching and tempering), attained percentage weight loss that was slightly lower than the SKH51-A. This could be due to the fact that the microstructure of the hardened steel tools, which consists mainly of austenitic and martensitic matrix, was more stable and more resistant to chemical reaction than that of the annealed steel tools, which consist mainly of ferritic (Pippel *et al.* 1999).

### Mechanical wearing of tool bits

The amount of mechanical wear was determined by the amount of knife-edge recession of the bit on the clearance face.

Oil palm wore the router bits faster compared with the other wood species (Figure 2). This was due to the higher content of silica in oil palm (Table 5).

Red meranti and pasang had the same silica content, but they were different in density (Tables 1 and 5). A higher wear rate of the bits when cutting pasang compared with red meranti could be due to the higher density of pasang. The clearance wear (Figure 2) and the wear rate (Table 7) of the M2 bit were twice larger than those of the tungsten carbide bits when cutting the same wood species.

Higher hardness of the K5 and K10 carbide bits compared with that of M2 (Table 3) was the reason. However, there was no significant difference in clearance wear and wear rate between the two carbide bits.

The results in Figure 3 gave an indication that wear patterns of the bits were the same for all wood species. Considering the results in the previous paper (Darmawan *et al.* 2001b) and that

**Table 5** Chemical characteristics of wood species

| Wood species | pH   | Extractive (%) | Ash (%) | Silica (%) |
|--------------|------|----------------|---------|------------|
| Coconut      | 5.82 | 8.3            | 1.8     | 0.2        |
| Oil palm     | 4.93 | 8.2            | 1.3     | 1.2        |
| Teak         | 4.10 | 10.9           | 1.4     | 0.4        |
| Red meranti  | 3.51 | 7.6            | 1.1     | 0.3        |
| Pasang       | 4.01 | 8.4            | 1.1     | 0.3        |

**Table 6** Percentage of weight loss of tool materials after 48 hours reaction at 80 °C with extractive and with wood powder solution

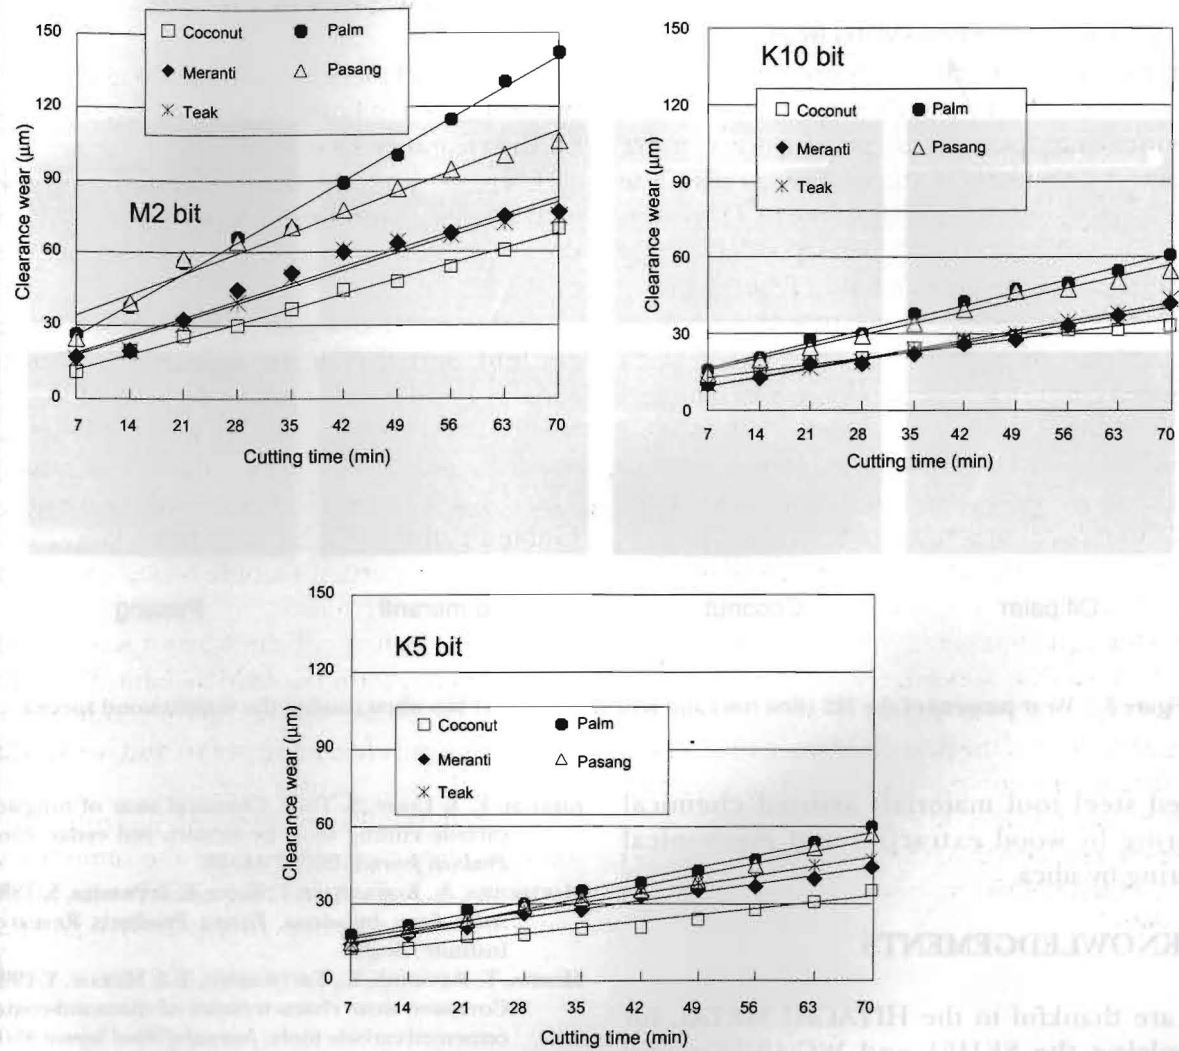


Figure 2 Clearance face wear of the bits as a function of cutting time for routing some tropical woods

Table 7 Rate of wear ( $\mu\text{m min}^{-1}$ ) of the router bits

| Bits | Wood species |          |      |             |        |
|------|--------------|----------|------|-------------|--------|
|      | Coconut      | Oil palm | Teak | Red meranti | Pasang |
| M2   | 0.88         | 1.81     | 1.01 | 1.01        | 1.21   |
| K5   | 0.34         | 0.64     | 0.51 | 0.46        | 0.64   |
| K10  | 0.36         | 0.70     | 0.51 | 0.40        | 0.66   |



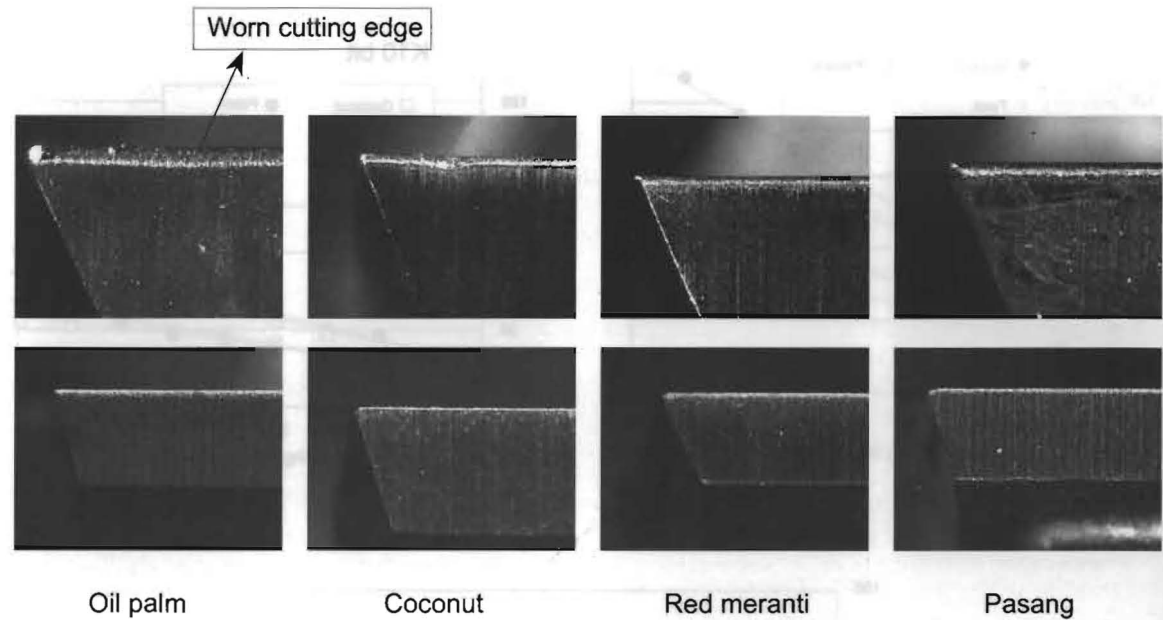


Figure 3 Wear patterns of the M2 (first row) and K10 (second row) bits when routing the various wood species

speed steel tool materials assisted chemical wearing by wood extractive and mechanical wearing by silica.

### ACKNOWLEDGEMENTS

We are thankful to the HITACHI METAL for supplying the SKH51 and WC-12%Co tool materials and to the KANEFUSA for preparing the M2 HSS and tungsten carbide bits for this study.

### REFERENCES

- DARMAWAN W., TANAKA, C., USUKI, H. & OHTANI, T. 2001a. Performance of coated carbide tool when grooving wood-based materials: effect of work materials and coating materials on the wear resistance of coated carbide tools. *Journal of Wood Science* 47(2): 94–101.
- DARMAWAN W., TANAKA C., USUKI H. & OHTANI T. 2001b. Performance of coated carbide tool when grooving wood-based materials: effect of work materials and coating materials on the wear resistance of coated carbide tools. *Journal of Wood Science* 47(2): 94–101.
- KIRBACH, E. & CHOW, S. 1976. Chemical wear of tungsten carbide cutting tools by western red cedar. *Forest Products Journal* 26(3): 44–48.
- MARTAWIJAYA, A., KARTASUJANA, I., KADIR, K. & PRAWIRA, S. 1989. *Atlas Kayu Indonesia*. Forest Products Research Institute, Bogor.
- MORITA, T., BANSHOYA, K., TSUTSUMOTO, T. & MURASE, Y. 1999. Corrosive wear characteristics of diamond-coated cemented carbide tools. *Journal of Wood Science* 45(6): 456–460.
- MURASE, Y. 1984. Effect of tool materials on the corrosive wear of wood-cutting tools. *Mokuzai Gakkaishi* 30(1): 47–54.
- PIPPEL, E., WOLTERS DORF, J., POCKL, G. & LICHTENEGGER, G. 1999. Microstructure and nanochemistry of carbide precipitates in high-speed steel S6-5-2-5. *Materials Characterization* 43(1): 41–55.
- PORANKIEWICZ, B. & GRÖNLUND, A. 1991. Tool wear-influencing factors. Pp. 220–229 in *Proceedings of the 10th International Wood Machining Seminar*. 21–23 October 1991, University of California, Richmond.
- TAPPI. 1991a. *Tappi Test Methods: Ash in Wood and Pulp (T 211 om-85)*. Volume 1. Tappi Press, Atlanta.